

## Nuclear Resonant Small-Angle Scattering of Nanoparticles

Yasuhiro KOBAYASHI<sup>\*1</sup>, Makoto SETO<sup>1</sup>, Shinji KITAO<sup>1</sup>, Ryo MASUDA<sup>2</sup>,  
Satoshi HIGASHITANIGUCHI<sup>1</sup>, ZHANG Xiaowei<sup>3</sup>

<sup>1</sup>Research Reactor Institute, Kyoto University, Kumatori, Osaka 590-0494, Japan

<sup>2</sup>Quantum Beam Science Directorate, Japan Atomic Energy Agency, Sayo, Hyogo 679-5148, Japan

<sup>3</sup>KEK-PF, Tsukuba, Ibaraki 305-0801, Japan

### Introduction

The nuclear forward scattering (NFS) is powerful technique to measure the hyperfine fields of the nuclear. On NFS measurement, we can use the X-ray optical technique. It is the advantage over the other hyperfine field measurement techniques. On this study, we used small-angle scattering technique with NFS. From the nuclear resonant small-angle scattering, we can obtain the information of the hyperfine field from the specific size scattering material [1].

### Experimental Procedure

The experimental arrangement is shown in Fig. 1. It is typical setting of Bonse-Hart camera. The energy of the synchrotron radiation was tuned into 14.4 keV and monochromatized into 6.4 meV width by the high-resonance monochromator. The angular profiles were measured by the rotation of second Si 111 channel cut monochromator. So far we have used two Si 111 monochromator upper and lower the sample. In this time, we used one Si 111 monochromator to analyze the scattering angle in order to suppress the loss of beam flux and to get more nuclear resonant scattering. The photons were detected by the Avalanche Photo Diode (APD), which is fast X-ray detector.

The sample was magnetic fluid, which is a mixture of Fe<sub>3</sub>O<sub>4</sub> nanoparticles and oil. The diameters of the particles were not controlled, so they were uneven, 10~200 nm. The Fe was enriched by <sup>57</sup>Fe. At the measurement, the sample was cooled at 80 K.

### Results and Discussion

The observed time spectra at the forward and the small angle (80  $\mu$ rad) are shown in Fig. 2. The two time spectra show same-period oscillation. This results shows that there is no difference between the hyperfine magnetic field of the whole of the sample and that of small particles in the samples. We could not observe the particle-size dependence of the hyperfine magnetic field.

### References

[1] Yu. V. Shvyd'ko et al., Phys. Rev. B, 54, 14942 (1996).

\*ykoba@rri.kyoto-u.ac.jp

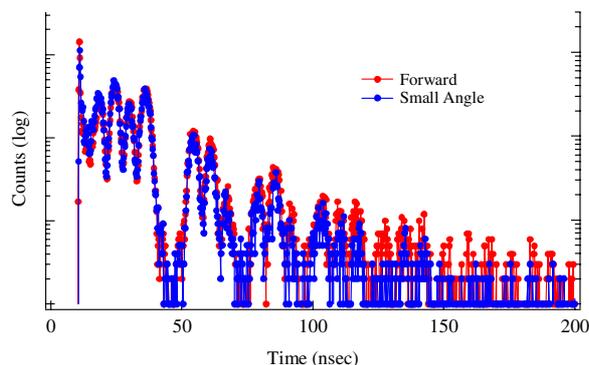


Fig. 2. The observed time spectra of Fe<sub>3</sub>O<sub>4</sub> nanoparticles at 80K.

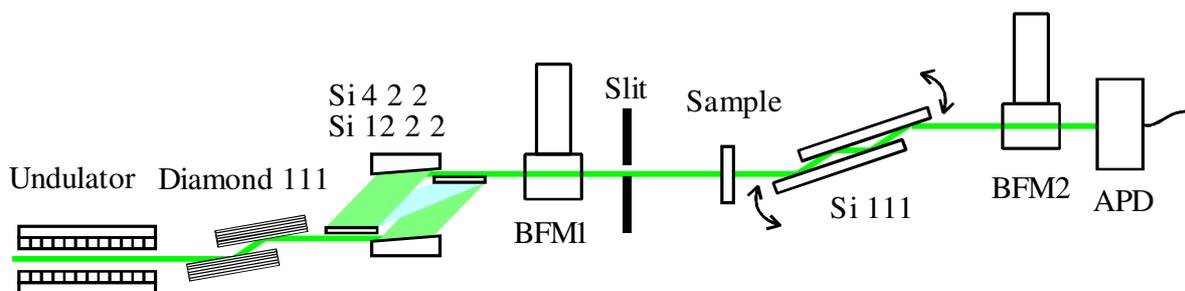


Fig. 1. Schematic drawing of experimental arrangement. Components are not in scale.