# **Applied Science**

# G-GIXS approach to characterize nano-structure of the titanium surface after chemical treatments (III)

Masao KIMURA<sup>1</sup>, Noriaki OHTA<sup>2</sup> and Michio KANEKO<sup>3</sup> <sup>1</sup> Adv. Tech. Res. Lab., Nippon Steel Corp., Futtsu, Chiba, 293-8511, Japan <sup>2</sup> Nippon Steel Technoresearch, Chiba 293-8500, Japan <sup>3</sup> Steel Res. Lab., Nippon Steel Corp., Futtsu, Chiba, 293-8511, Japan

## **Introduction**

Titanium sheets have been applied for roofs, walls and monuments for more than 10 years even in seaside where stainless steels may suffer pitting corrosion. However, titanium shows discoloration phenomenon in some cases, where a thin titanium oxide film forms on the surface resulting in change of colour caused by interferential colouring depending on thickness of the film. Though it does not deteriorate durability of titanium sheets for exterior materials, it might spoil outward appearance.

Recently it has shown that chemical treatments of titanium sheets are effective for preventing the discoloration of titanium [1,2]. But its mechanism has not been clarified yet because of difficulty to reveal the change of surface after chemical treatments. We have applied generalized grazing-incidence-angle x-ray scattering (G-GIXS) technique [3] to investigate the change in surface structure by chemical treatments [4].

#### **Experiments**

The surface of titanium sheet was chemically treated using a solution of HNO<sub>3</sub>+HF. The surface was analyzed by x-ray photoelectron microscopy (XPS) to determine the thickness and the chemical compositions. Then the nano-scale structure of the surface was investigated by G-GIXS, where symmetric and non-symmetric diffraction intensities are measured simultaneously with keeping the incident angle ( $\alpha_i$ ) near the critical angle ( $\alpha_c$ ) of total reflection. G-GIXS measurements were carried out at BL-6C at PF, KEK, Tsukuba, Japan. Diffraction patterns were measured in air using a scintillation detector and an image plate with an x-ray of 9.54 keV. Details of conditions were described in the reference [3].

## **Results and Discussion**

XPS has shown that the surface of specimen was covered with a thin (ca. few nm) titanium oxide film containing fluorine (F). However, no clear relationship has been shown between the chemical compositions of the films and their discoloration properties.

G-GIXS measurements were carried out for various incident angles ( $\alpha_i$ ), and the broad peaks were clearly observed in the pattern. Atomic correlation was obtained, corresponding to anatase-type of TiO<sub>2</sub> phase (Fig.1). Diffraction patterns obtained by G-GIXS showed slight but significant differences among specimens which were

treated by solutions with different ratios of  $HNO_3/HF$ . The width of diffraction peak becomes small when the ratio of  $HNO_3/HF=1/0$ . These results suggest that chemical treatment with  $HNO_3$  results in formation of oxide layer with high correlation in arrangements of Ti-O units.

It has been shown that G-GIXS approach can give fundamental understanding the mechanism of chemical treatments of titanium surface. Recently this technique has been applied to study on discoloration resistance of colored titanium sheets [5].

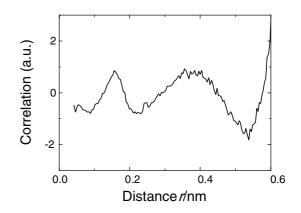


Fig.1 Atomic correlation obtained for titanium sheet which was chemically treated using a solution of  $HNO_3$ +HF.

### **References**

[1] M. Kaneko, K. Takahashi, T. Hayashi, I. Muto, K. Tokuno and K. Kimura: Proc. 15th International Corrosion Congress,

Granada, Spain, Paper No. 26, (2002).

[2] K. Takahashi, M. Kaneko, T. Hayashi, J. Tamenari, and H. Shimizu: Proc. Ti-2003 Science and Technology, Hamburg, 3117, (2004).

[3] M. Kimura, A. Acosta, H. Fujioka, M. Oshima: J. Appl. Phys., 93, 2034-2040 (2003)

[4] M. Kimura et al: PF Act. Rep. #26 Part B, p.239 (2009).

[5] M. Kimura, M. Kaneko, K. Tokuno: Corr. Sci., 52, 1889-1896 (2010)